

1-16 What Has Formed from the Melted Fuel and Control Blade?

- Investigating the Characteristics of Solidified Core Melt -

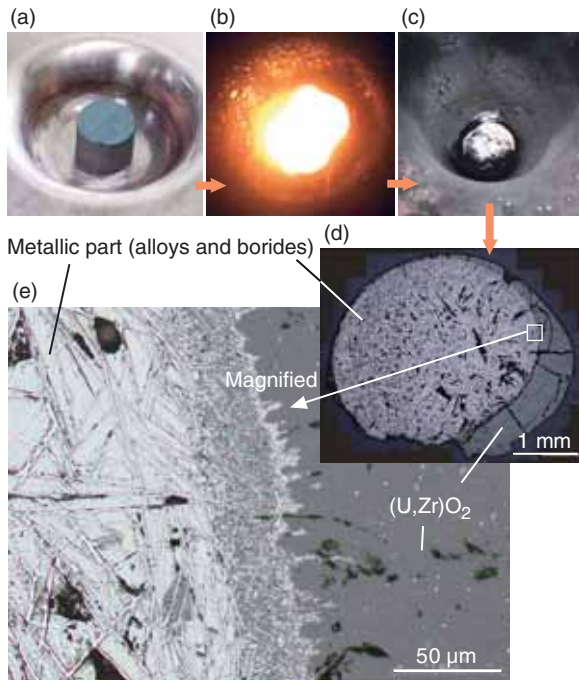


Fig.1-34 The appearance and cross-sectional images of a solidified melt specimens

Photos (a)–(c) show the starting mixture, melted state, and solidified button, respectively. (d) and (e) are the microphotographs of the cross section. The needle-like precipitation of crystalline ZrB_2 is found in the metallic part.

For the decommissioning of the accident at the TEPCO's Fukushima Daiichi NPS (1F), the removal of fuel debris and its appropriate management are imperative missions. Therefore, we have been studying the characteristics of fuel debris using simulated specimens.

The fuel debris formed in the reactor cores mainly comprises materials from the fuel (UO_2 and Zr) and control blade (B_4C and stainless steel). However, the chemical form of boron in the fuel debris has not been well identified.

To simulate the solidified fuel debris in the reactor cores, some pelletized mixtures of B_4C , stainless steel, Zr, and $(U,Zr)O_2$ (a mixed oxide of UO_2 and ZrO_2) were arc-melted under an Ar atmosphere, as shown in photos (a)–(c) of Fig.1-34. The chemical forms in the solidified specimens were analyzed along the cross section (photos (d) and (e)). The specimens likely consist of $(U,Zr)O_2$ ceramic part and metallic part. The latter is found to include the precipitation of borides expressed as ZrB_2 and $(Fe,Cr,Ni)_2B$ in the alloy matrix of Fe-Cr-Ni and

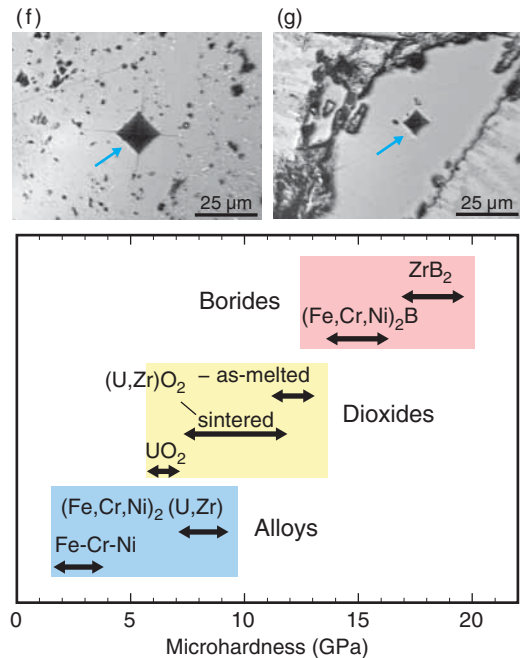


Fig.1-35 Comparison of the microhardnesses of phases in the solidified melt specimens

Photos (f) and (g) show examples of indentation on $(U_{0.5}Zr_{0.5})O_2$ and ZrB_2 , respectively. Hardness increases in the order of alloys, dioxides, and borides.

$(Fe,Cr,Ni)_2(Zr,U)$ intermetallic.

To examine the influence of oxygen in the atmosphere, the solidified specimens were annealed at $1500\text{ }^\circ\text{C}$ in an Ar- $0.1\%O_2$ mixed gas flow for 10 h. Consequently, the Zr and U in the alloy, and the Zr in ZrB_2 were oxidized to form a Zr-rich $(Zr,U)O_2$ layer on the surface. The boron isolated from ZrB_2 alternatively formed $(Fe,Cr,Ni)_2B$ inside the oxide layer.

As a basic mechanical property of fuel debris, the microhardnesses of the phases in the specimen were measured by a Vickers tester (Fig.1-35). It is found that the borides, especially ZrB_2 , are extremely hard compounds in all the phases. The dense precipitation of borides in the fuel debris may potentially be a barrier against machining tools for removal operations.

The present study was sponsored by the Agency for Natural Resources and Energy, Ministry of Economy, Trade and Industry of Japan (METI).

Reference

Takano, M. et al., Characterization of Solidified Melt among Materials of UO_2 Fuel and B_4C Control Blade, Journal of Nuclear Science and Technology, vol.51, issues 7-8, 2014, p.859-875.