

9-11 Corrosion Inhibition using a Small Amount of Oxygen

— Effect of Dissolved Oxygen on the Corrosion Properties of a Blanket Structural Material —

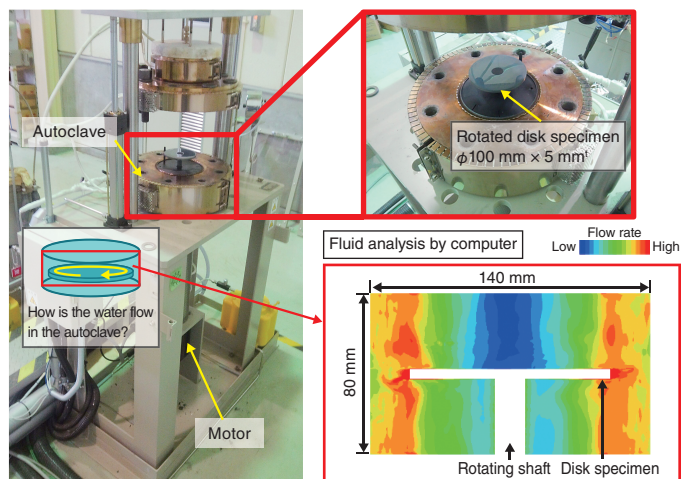


Fig.9-28 Appearance of a corrosion test apparatus for a rotated disc specimen

A rotated disk specimen has been tested in high-temperature pressurized water to investigate the flow-assisted corrosion of structural material for the fusion blanket. The flow speed distribution around the disc specimen has been visualized using computational fluid dynamics.

A fusion blanket is a component surrounding fusion plasma and converts fusion energy into thermal energy using high-temperature pressurized water as a coolant. It is important to investigate the corrosion behavior of a structural material for robust design of a blanket. Since the coolant water has a maximum flow rate of 5 m/s, it is worrisome that corrosion will be accelerated by the flow. Therefore, we developed a corrosion test apparatus for a rotated disc specimen to simulate the water flow condition in the blanket (Fig.9-28). We performed the corrosion test in flowing high-temperature water using this apparatus.

Based on the results obtained from the corrosion test under various dissolved oxygen (DO) concentrations (Fig.9-29), all the specimens demonstrated a weight gain after the corrosion test without the water flow. This was caused by oxidation of the specimen. On the contrary, weight loss was observed after corrosion tests under a water flow condition and was significant when DO concentrations were low. By increasing the DO concentration up to 8 mg/ℓ, the weight loss was

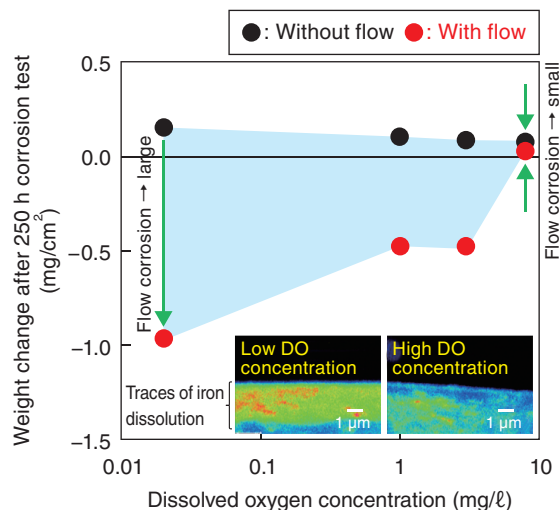


Fig.9-29 Relation between dissolved oxygen concentration and weight change (degree of corrosion) after corrosion test of 250 h

A small amount of oxygen in water (DO) has drastically reduced the effect of flow on corrosion properties (■). Iron dissolution is hardly observed on the specimen tested at an 8 mg/ℓ DO concentration.

successfully suppressed and so was the flow-assisted corrosion (■ in Fig.9-29).

For a clear understanding, a cross-sectional observation of the specimen was conducted. The thick iron-poor layer that formed as a result of the dissolution of iron was observed on the specimen under lower DO concentration, while there was no thick iron-poor layer on it under higher DO concentration. Therefore it is believed that the dissolution of iron caused the weight loss. Based on the microstructural observation of the corrosion product, it was considered that the dissolution of iron was suppressed by forming hematite as corrosion-resistant oxide on the surface of the specimen tested with high-DO water.

Since water flow corrosion was inhibited by inputting a small amount of dissolved oxygen, we obtained an outlook for water conditioning that demonstrates less corrosion. These results contribute to the determination of cooling water conditions for the fusion blanket and bring us one step closer to the realization of a fusion reactor.

Reference

Nakajima, M. et al., Corrosion Properties of F82H in Flowing High Temperature Pressurized Water, Journal of Plasma and Fusion Research SERIES, vol.11, 2015, p.69-72.